

# Mechanistic Insights into Electrochemical Reduction of CO<sub>2</sub> over Ag using DFT and Transport Models

**Classification:** Physical Sciences

Meenesh R. Singh<sup>1,2†</sup>, Jason D. Goodpaster<sup>1,2,†</sup>, Adam Z. Weber<sup>1</sup>, Martin Head-Gordon<sup>1,4</sup>, and Alexis T. Bell<sup>1,5,\*</sup>

<sup>1</sup>Joint Center for Artificial Photosynthesis, Lawrence Berkeley National Laboratory, Berkeley, CA 94720

<sup>2</sup>Department of Chemical Engineering, University of Illinois at Chicago, Chicago, IL 60607

<sup>3</sup>Department of Chemistry, University of Minnesota, Minneapolis, MN 55455

<sup>4</sup>Department of Chemistry, University of California Berkeley, Berkeley, CA 94720

<sup>5</sup>Department of Chemical and Biomolecular Engineering, University of California Berkeley, Berkeley, CA 94720

Submitted to PNAS

† Authors Contributed Equally

## Corresponding Author:

Professor Alexis T. Bell  
The Dow Professor of Sustainable Chemistry  
Department of Chemical & Biomolecular Engineering  
107 Gilman Hall  
University of California  
Berkeley, CA 94720-1462  
Tel: (510) 642-1536  
Email: alexbell@berkeley.edu

**Keywords:** Electrochemical Reduction of CO<sub>2</sub>, Density Functional Theory, Microkinetic Model, Transport Model, CO Production over Ag

## Abstract

Electrochemical reduction of CO<sub>2</sub> using renewable sources of electrical energy holds promise for converting CO<sub>2</sub> to fuels and chemicals. Since this process is complex and involves a large number of species and physical phenomena, a comprehensive understanding of the factors controlling product distribution is required. While the most plausible reaction pathway is usually identified from quantum chemical calculation of the lowest free energy pathway, this approach can be misleading when coverages of adsorbed species determined for alternative mechanism differ significantly, since elementary reaction rates depend on the product of the rate coefficient and the coverage of species involved in the reaction. Moreover, cathode polarization can influence the kinetics of CO<sub>2</sub> reduction. Here we present a multiscale framework for *ab initio* simulation of the electrochemical reduction of CO<sub>2</sub> over an Ag(110) surface. A continuum model for species transport is combined with a microkinetic model for the cathode reaction dynamics. Free energies of activation for all elementary reactions are determined from density functional theory calculations. Using this approach, three alternative mechanisms for CO<sub>2</sub> reduction were examined. The rate-limiting step in each mechanism is  $\ast\ast\text{COOH}$  formation at higher negative potentials. However, only via the multiscale simulation was it possible to identify the mechanism that leads to a dependence of the rate of CO formation on the partial pressure of CO<sub>2</sub> that is consistent with experiments. Simulations based on this mechanism also describe the dependence of the H<sub>2</sub> and CO current densities on cathode voltage that are in strikingly good agreement with experimental observation.

## Significance Statement

Chemical storage of solar energy can be achieved by electrochemical reduction of CO<sub>2</sub> to CO and H<sub>2</sub>, and subsequent conversion of this mixture to fuels. Identifying optimal conditions for electrochemical cell operation requires knowledge of the CO<sub>2</sub> reduction mechanism and the influence of all factors controlling cell performance. We report a multiscale model for predicting the current densities for H<sub>2</sub> and CO formation from first principles. Our approach brings together a quantum chemical analysis of the reaction pathway, a microkinetic model of the reaction dynamics, and a continuum model for mass transport of all species through the electrolyte. This model is essential for identifying a physically correct representation of product current densities dependence on the cell voltage and CO<sub>2</sub> partial pressure.

\body


## 1. Introduction

The electrochemical reduction of CO<sub>2</sub> to fuels is a subject of considerable interest because it offers a means for storing electricity from intermittent energy sources (e.g., wind and solar radiation) in the form of chemical bonds(1-3). An attractive strategy to this end involves the electrochemical production of CO by the CO<sub>2</sub> reduction reaction (CO<sub>2</sub>RR) and the production of H<sub>2</sub> by the hydrogen evolution reaction (HER). Proper choice of catalyst and operating conditions (4, 5) enables attainment of optimal performance of the electrochemical cell for each of these reactions. Since CO and H<sub>2</sub> are insoluble gases, they can be readily separated from an aqueous electrolyte (6) and the resulting mixture, known as synthesis gas, can be converted to fuels such as methanol, dimethyl ether, or a mixture of hydrocarbons using known technologies (7). The overall kinetics of the CO<sub>2</sub>RR depend on many factors (8), including details of the catalyst (9-12), electrolyte composition (13-16) and pH (17), the membrane separating the anolyte and catholyte, temperature (18, 19), CO<sub>2</sub> partial pressure (20), cell dimensions (19), and applied potential. Therefore, it is highly desirable to develop a model that can simulate the performance of the electrochemical cell so that the influence of each variable on cell performance can be identified. Such a model can also be used to assess whether the mechanism chosen to represent the kinetics of the CO<sub>2</sub>RR is consistent with experimental data. The present work was undertaken for this purpose.

Electrocatalysts such as Au, Ag, Zn, Pd, and Ga are known to yield mixtures of CO and H<sub>2</sub> at varying ratios depending on the applied voltage (21-25). The electrocatalysts exhibiting the highest activity and selectivity to CO vs H<sub>2</sub> are Au and Ag. Since Ag is much more abundant and less expensive than Au, Ag is the more promising electrocatalyst for large-scale production of CO. The CO<sub>2</sub>RR to CO and H<sub>2</sub>O requires two electrons and two protons, which are supplied by recombination of an electron with a proton or with water, in which case OH<sup>-</sup> is also produced as a byproduct (26). Although there exist low overpotential electrocatalysts for CO formation (12, 27), Ag was used in this study due to availability of i) experimental data on current density of CO and H<sub>2</sub> versus applied potential and partial pressure of CO<sub>2</sub> and ii) well-defined catalyst interface and cell parameters used in the experiments.

Various mechanisms for CO<sub>2</sub> reduction over Ag have been discussed in the literature. The earliest of these proposes that the first step of the reaction sequence involves the formation of a radical anion (CO<sub>2</sub><sup>•-</sup>) at the catalyst surface (28). While the onset potential for CO formation over Ag is higher (more positive) than the equilibrium potential of -1.9 V vs NHE for CO<sub>2</sub><sup>•-</sup> formation (29), Hori and coworkers (28) have proposed that adsorbed CO<sub>2</sub><sup>•-</sup> could be stabilized at potentials higher than -1.9 V by back donation of electrons from the highest occupied *d* orbital of 1B elements such as Ag to the lowest unoccupied anti-bonding ( $\pi^*$ ) orbital of CO<sub>2</sub><sup>•-</sup>. They also noted that the adsorbed CO<sub>2</sub><sup>•-</sup> is chemically equivalent to adsorbed CO<sub>2</sub><sup>-</sup>.


(i.e.  $^{*}\text{CO}_2^{-}$ ), since the free electron associated with the radical anion will be donated to the unoccupied metal orbital. The bent structure of adsorbed  $\text{CO}_2^{\bullet-}$  not only lowers the energy for electron transfer but also facilitates hydrogenation of the O atom interacting with the catalyst surface to produce CO via the sequence of steps shown in reaction 1 (28).




A reaction pathway to CO not involving  $^{*}\text{COOH}$  has been proposed by Ikeda et al., who envision that CO is produced over Ag by dissociation of adsorbed  $\text{CO}_2^{\bullet-}$  (30).




Another alternative for the path to CO has been proposed by Savéant and coworkers, who suggest that in non-aqueous electrolytes a  $\text{CO}_2\text{-CO}_2^{\bullet-}$  adduct can form which upon disproportionation yields CO and  $\text{CO}_3^{2-}$  (31).




Mechanisms not involving the formation of  $\text{CO}_2^{\bullet-}$  as the first intermediate have also been suggested for Ag. Kostecki and Augustynski have proposed that hydrated  $\text{CO}_2$  is reduced to dihydroxycarbene which then undergoes dehydration to produce CO (32).



Mechanisms not involving the formation of an adsorbed anion or radical anion have been considered as well. Jiao and coworkers have claimed that  $\text{CO}_2$  can be electrochemically reduced with  $\text{HCO}_3^{-}$  to produce CO over Ag (33).



And Jaramillo and coworkers have suggested that the simultaneous transfer of a proton and an electron to aqueous  $\text{CO}_2$  produces  $^{*}\text{COOH}$  on Ag, which in turn yields CO after another electron and proton transfer (9).



A mechanism similar to reaction 6 but involving proton-coupled electron transfer to the adsorbed  $\text{CO}_2$  has also been envisioned (26).

It is notable that the pathways for  $\text{CO}_2$  reduction to CO over Ag discussed above are all based on chemical intuition, but for the most part, these schemes have not been validated by means of theoretical analysis, spectroscopic observations of proposed intermediates, or full

microkinetic analysis. An exception to this perspective is the recent work of Nørskov and coworkers (34). Their DFT calculations for the energetics of CO<sub>2</sub>RR over Ag(111) support a scheme similar to reaction 1. Gas phase CO<sub>2</sub> is assumed to be in equilibrium with \*CO<sub>2</sub> that reduces to \*COOH and the rate-limiting step is taken to be the reduction of \*COOH. Operando spectroscopic support for the presence of the adsorbed species appearing in reactions 1-6 has proven to be very difficult due to the low coverages of these species and interference from gas bubbles; consequently, only limited information has been reported. Surface-enhanced Raman spectra of a polycrystalline Ag surface acquired during CO<sub>2</sub> reduction exhibit bands for adsorbed water, CO, HCOO<sup>-</sup> and Ag-CO<sub>2</sub> under reducing potentials. The frequency of these bands shift to lower wavenumbers and their intensity increases with decreasing applied potential (35, 36). Recently, IR spectroscopy has been used to observe the species present on Ag films during CO<sub>2</sub> reduction. Evidence for adsorbed CO<sub>2</sub><sup>-</sup>, HCOOH, and CO has been obtained by this means (37). Although these findings support the presence of the carbon-containing species on Ag films proposed to be present during the electrochemical reduction of CO<sub>2</sub>, the elementary steps by which they are formed were not revealed. Therefore, several open questions remain regarding the mechanism of the CO<sub>2</sub>RR over Ag - i) What are the key intermediates involved in the CO<sub>2</sub>RR? ii) How does the HER occur? iii) Which hydrogen species participate in the CO<sub>2</sub>RR?, iv) How do the free energies of adsorption and reaction, and the free energy barriers for the elementary reaction involved in the CO<sub>2</sub>RR vary with the applied potential? v) How do the mass transport of species, such as CO<sub>2</sub>, HCO<sub>3</sub><sup>-</sup>, CO<sub>3</sub><sup>2-</sup>, K<sup>+</sup>, H<sup>+</sup>, and OH<sup>-</sup>, and cathode polarization affect the product distribution? vi) How do rates of CO and H<sub>2</sub> evolution at the Ag cathode affect the rate of reaction? vii) What are the rate-limiting reactions for the CO<sub>2</sub>RR and the HER over Ag?

The aim of the present study is to develop a multiscale, multiphysics model of the electrochemical reduction of CO<sub>2</sub> on Ag that can be used to predict the partial currents of CO and H<sub>2</sub> produced as functions of the applied potential and partial pressure of CO<sub>2</sub>. The free energies of activation for each elementary step involved in three proposed pathways for CO<sub>2</sub> reduction are determined from density functional theory (DFT) calculations. This information is used to determine the equilibrium constants and rate coefficients for each elementary step occurring on the cathode surface as a function of applied potential. The rate parameters, cathode CO<sub>2</sub> concentration, and cathode pH are used in a microkinetic model to calculate rates of formation of CO and H<sub>2</sub>. The rates of reactant consumption and product formation obtained from a microkinetic model are used as boundary conditions for a continuum model describing the transport of all species through the electrolyte and to determine the concentrations of neutral and ionic species present at the cathode and anode surfaces. We demonstrate that through the use of this multiscale, multiphysics model it is possible to predict a dependence of the partial current densities of CO and H<sub>2</sub> on the cathode voltage and the CO<sub>2</sub> partial pressure that is in agreement with what is observed experimentally (9). We also demonstrate that by simulating the full reaction dynamics it is possible to identify which of the three proposed mechanisms for the

electrochemical reduction of CO<sub>2</sub> on Ag is most physically consistent with experimental observations.

## 2. Theory

### 2.1 Continuum Transport Model

Figure 1(a) shows a schematic of the electrochemical cell that was simulated. The cell dimensions and the compositions of the electrodes, electrolyte, and membrane separator were chosen to be identical to those used in the experimental work of Hatsukade et al. (9). The anode and cathode are Pt and Ag, respectively, and are separated by a distance of ~ 3.56 cm. A 100 μm thick anion-exchange membrane (Selemion AMV) is located half way between the two electrodes. The electrolyte is 0.1 M KHCO<sub>3</sub> (pH 6.8) continuously sparged with 20 sccm of CO<sub>2</sub> gas at ambient conditions. Most aqueous-phase CO<sub>2</sub>RR studies reported in the literature are conducted in 0.1 M KHCO<sub>3</sub> (pH 6.8) as higher concentrations of KHCO<sub>3</sub> favor HER over CO<sub>2</sub>RR (38). This effect is due to screening of electric field in the concentrated electrolyte (8), which destabilizes the CO<sub>2</sub>RR intermediates and thereby reduces the Faradaic efficiency (34). The anolyte and catholyte are assumed to be well mixed by the sparged CO<sub>2</sub> and to offer no diffusion resistances. The only resistances to mass transfer are assumed to occur in the ~ 40 μm-thick hydrodynamic boundary layer present next to each of the electrodes and in the membrane separator. The hydrodynamic boundary layer was estimated based on the limiting current density of 22 mA cm<sup>-2</sup> (8). Such small limiting current densities are a consequence of lower solubility of CO<sub>2</sub> (33 mM) and lower buffer concentration (0.1 M) in the aqueous electrolyte.

Since the concentration of the electrolyte is < 1 mol%, dilute solution theory was used in the Nernst-Planck equations to model diffusion, migration, and bulk reactions (water and buffer dissociation) of species in the electrolyte and the membrane. Ionic species such as HCO<sub>3</sub><sup>-</sup>, CO<sub>3</sub><sup>2-</sup>, K<sup>+</sup>, H<sup>+</sup>, and OH<sup>-</sup>; and the neutral species such as CO<sub>2</sub>, CO, and H<sub>2</sub> were considered in the continuum model. The anion exchange membrane (AEM) was modeled as an electrolyte with fixed background positive charge concentration of ~1 M, which is similar to ~1.9 mequiv/g of ion exchange capacity of Selemion AMV (39). The diffusion coefficients of anions such as HCO<sub>3</sub><sup>-</sup>, CO<sub>3</sub><sup>2-</sup>, and OH<sup>-</sup> in a hydrated AEM is typically an order of magnitude lower than in an aqueous electrolyte (40). Since the diffusion coefficients of cations in an AEM are not available, we have assumed their values to be two orders of magnitude lower than those used for transport in the electrolyte. This assumption is based on experimental observation of similar order of magnitude reduction of counter-ion diffusion in a cation-exchange membrane (41, 42). The lower diffusion coefficient of H<sup>+</sup> in AEM does not affect the pH gradient in the electrolyte, since the majority charge carriers, such as HCO<sub>3</sub><sup>-</sup> and CO<sub>3</sub><sup>2-</sup>, can be transported effectively through the membrane (8). The kinetics of water oxidation over Pt was modeled using the Butler-Volmer expression (43). The kinetics of CO<sub>2</sub>RR was modeled using the microkinetic

model described in Section 2.2. An overview of the continuum transport model is given in the Section S1 of the Supplementary Information. The continuum transport model was solved using COMSOL Multiphysics to obtain a concentration of CO<sub>2</sub> and pH at the cathode as a function of the product current densities.

## 2.2 Microkinetic Model

Figure 1(b) shows an example of the microkinetic model for CO<sub>2</sub>RR and HER over Ag(110), which is the most active facet of Ag.(10) The primary source of hydrogen for the HER is H<sub>2</sub>O, as the concentration of H<sup>+</sup> is at least eight orders of magnitude lower than the concentration of H<sub>2</sub>O in neutral-pH electrolytes. The first elementary step of HER is taken to be the Volmer reaction, in which either free or adsorbed H<sub>2</sub>O is reduced to an H atom adsorbed on Ag(110) and an OH<sup>-</sup> anion released into the electrolyte. The second elementary step of the HER can occur via either the Tafel or the Heyrovsky reaction. The Tafel reaction involves reaction of two adsorbed H atoms to form H<sub>2</sub>, whereas the Heyrovsky reaction involves the reaction of free H<sub>2</sub>O with the adsorbed H atom to produce H<sub>2</sub> and the release of an OH<sup>-</sup> anion into the electrolyte. The computed energy barrier for Tafel reaction was at least 0.4 eV higher than that for the Heyrovsky reaction. Therefore, the Volmer-Heyrovsky mechanism shown in Figure 2a-c was used to model the HER.

The reduction of CO<sub>2</sub> to form CO occurs via two steps. In the first step, CO<sub>2</sub> adsorbs, so that the C atom binds with the Ag atom in the troughs of the (110) facets (see Figure S5A). Adsorbed CO<sub>2</sub> (\*CO<sub>2</sub>) then reacts with an atom of H to form adsorbed COOH (\*\*COOH). \*\*COOH denotes two-fold coordination to the surface, through C as in \*CO<sub>2</sub> and also through H coordinated to another Ag site across the ridge. In the second step, \*\*COOH reacts with a second H atom to form adsorbed CO (\*CO), and H<sub>2</sub>O. The C atom of \*CO binds with a Ag atom, resulting in a vertical orientation. As shown in Figure 2a-c, the H atoms required for the reduction of CO<sub>2</sub> can come from adsorbed H (\*H), adsorbed H<sub>2</sub>O (\*\*H<sub>2</sub>O, in which two H atoms bind with two Ag atoms across the trough of a (110) facet), or from free H<sub>2</sub>O. Activation of \*CO<sub>2</sub> to form \*CO<sub>2</sub><sup>-</sup> prior to hydrogenation was also considered.

The rate coefficients for all elementary reactions were modeled using transition-state theory. The potential-dependent Gibbs free energies of adsorption for CO<sub>2</sub>, CO, H<sub>2</sub>, and H<sub>2</sub>O, and the Gibbs free energies of activation for all elementary reactions were obtained from the DFT calculations described in Section 2.3. Since the rates of electrocatalytic reactions are much lower than the rates of adsorption/desorption, the adsorbed reactants (CO<sub>2</sub> and H<sub>2</sub>O), and the adsorbed products (H<sub>2</sub> and CO) are assumed to be in quasi-equilibrium with their concentrations in the electrolyte. The activity of H<sub>2</sub>O near the cathode was assumed to be 1.0 and the activity of dissolved CO<sub>2</sub> and OH<sup>-</sup> are obtained from the continuum model. The activities of dissolved CO and H<sub>2</sub> near the cathode are determined from the fractional current densities of CO and H<sub>2</sub>, respectively.

The microkinetic model considers adsorption and desorption of reactants and products, and the elementary surface reactions. Figure 1(b) shows this model involves a total of 10 reactions and 8 species. Therefore, the local concentration of CO<sub>2</sub> and pH near cathode needs to be specified using the continuum model in order to fully describe the system. Given the initial concentration of CO<sub>2</sub> in the electrolyte and the bulk pH of the electrolyte, the microkinetic model predicts the partial current densities of products, which are then supplied to the continuum model in order to obtain the concentration of CO<sub>2</sub> and pH near the cathode. These calculations are repeated until species concentrations and current densities converge. Details of the microkinetic model are given in the Section S2 of the Supplementary Information. The equations representing the microkinetic model were solved using MATLAB.

### 2.3 Kohn-Sham Density Functional Theory


Figure 1(c) shows the simulation cell used for the DFT calculations. It consists of a 3 x 3 x 4 atom cell representing the Ag(110) surface. This cell ensures that there is a minimum of 5 Å between adsorbates, which minimizes the interaction between periodic images. Free energy calculations were performed in two steps. First, 5ps of *ab initio* molecular dynamics were performed using 72 explicit water molecules, the reaction intermediate, and surface atoms to generate a reasonable water configuration. Subsequently, 36 of the water molecules were removed from the top layer and replaced by an implicit electrolyte. The solvent was treated as a continuum dielectric and the electrolyte was described by a linearized Poisson-Boltzmann model.(44, 45) The electrode potential was calculated from the Fermi energy. Since the Fermi energy can be varied by changing the number of electrons in the simulation cell, the electrochemical potential was set by calculating the number of electrons the simulation cell required for a specific Fermi energy. The simulation cell remains neutral as the linearized Poisson-Boltzmann model provides a charge compensation. Using this approach, the potential-dependent free energy reaction barriers and free energy of reactions were calculated, following the procedure detailed in Ref. (46). In our constant potential model, electrons are transferred when the atomic configuration dictates that an electron transfer (or partial electron transfer) needs to occur to maintain the applied potential. In essence, this assumes that electron transfer is not limiting the reaction and that a chemical step is the barrier to reduction. Therefore, only two types of steps need to be considered: (1) changes in the geometry of adsorbed species due to changes in the overpotentials, which result in activated adsorbed species prior to proton/hydrogen transfers and (2) proton/hydrogen transfers.

All calculations used the M06-L exchange-correlation functional as this functional provided good agreement between the calculated and measured heats of adsorption(47) of CO from the gas phase for small molecules on Ag(110), and has been shown to be reliable for barrier heights(48, 49). The energy profiles were obtained for potentials -0.0132 to -1.132 V vs RHE at an interval of 0.1 V using a modified version of Vienna *ab initio* simulation program (VASP). Since these energy barriers were obtained for a very low coverage, we have scaled the barriers to




account for the effects due to adsorbate-adsorbate interactions at high coverages and errors intrinsic to the exchange/correlation functional used in the DFT calculations. The measured current densities from -0.6 to -0.65 V vs RHE were used to scale the barriers such that the ratio of forward-barriers of the two elementary reactions does not change. The scaled barriers were higher than the original barriers by ~0.15-0.23 V, which is within the error of DFT calculations (50). Additional details are provided in Section S3 of the Supplemental Information.

**(a) Continuum Transport Model**

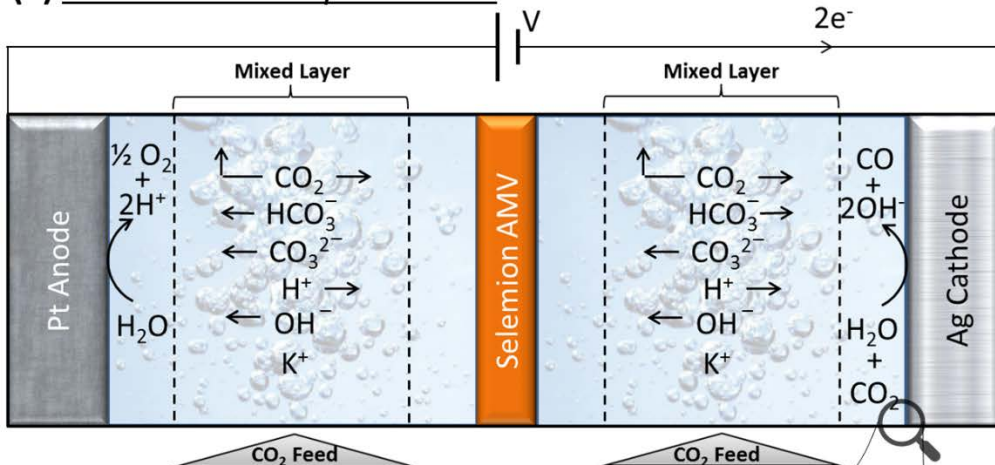

**(b) Microkinetic Model**

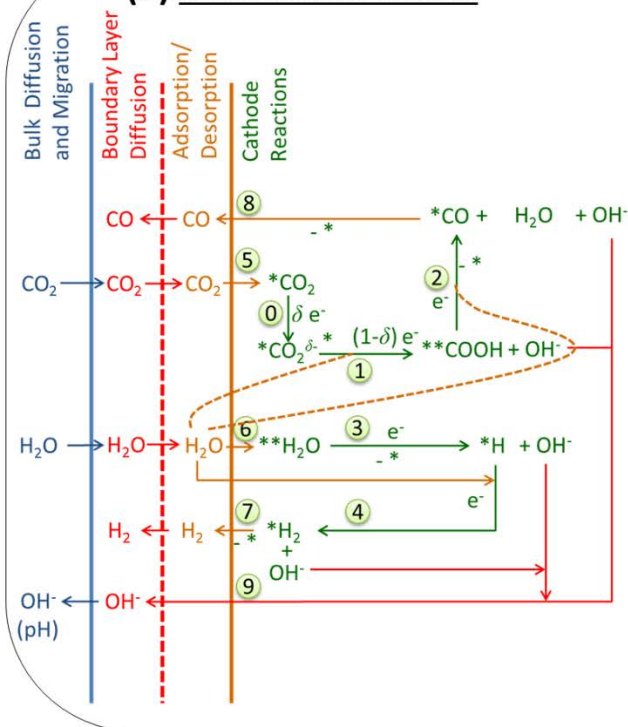

**(c) KS-DFT Model**

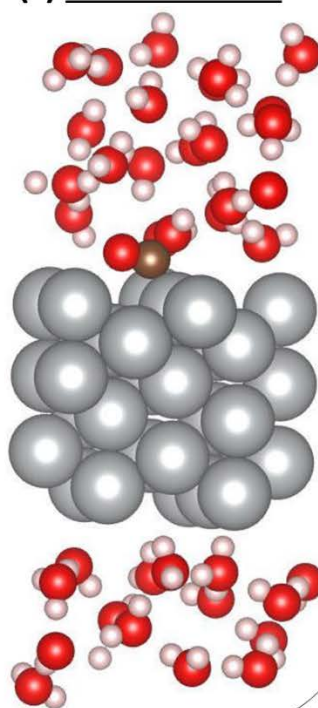


Figure 1: (a) Continuum model for species transport and reaction in a 1-D electrochemical cell for CO<sub>2</sub> reduction. The electrochemical cell contains 8 ml of 0.1 M KHCO<sub>3</sub> on each side of a 100  $\mu$ m-thick Selemion AMV membrane and is continuously sparged with 20 cm<sup>3</sup> min<sup>-1</sup> of CO<sub>2</sub>. The distance between the Pt anode and Ag cathode is ~3.56 cm, and the boundary layer thickness is 40  $\mu$ m. (b) Microkinetic model showing elementary processes for CO<sub>2</sub>RR and HER over Ag(110), which is coupled with the continuum model. (c) Kohn-Sham (KS) DFT model with explicit water layers to calculate energies of adsorbates, intermediates, and reaction barriers, which are supplied to the microkinetic model.

## 2.4 Multiscale Simulation

Since simulation of the continuum model, the microkinetic model, and the DFT model require different software, we have used a look-up table approach to integrate these models and solve them iteratively in order to calculate surface coverages and partial current densities of CO and H<sub>2</sub>. A table of pH and CO<sub>2</sub> concentration at cathode for a range of partial current densities was prepared using COMSOL Multiphysics. Another table of bonding energies of adsorbates and reaction barriers at different applied potentials was obtained from VASP. The multiscale simulations were performed in MATLAB where the microkinetic model was solved iteratively using these tables from COMSOL and VASP. The multiscale simulation scheme is discussed in Section S4 of the Supplementary Information. The first step in the simulation was to obtain rate parameters at an applied potential using the DFT model. The initial concentration of CO<sub>2</sub> and pH at the cathode were assumed to those in the bulk electrolyte and thereafter used in the microkinetic model along with the rate parameters to obtain the partial current densities of CO and H<sub>2</sub>. These current densities were then supplied to the continuum model to obtain CO<sub>2</sub> concentration and pH at the cathode. All the previous steps were iterated until the values of CO<sub>2</sub> concentration and pH at the cathode are converged. A convergence in the values of CO<sub>2</sub> concentration and pH of  $1 \times 10^{-3}$  was obtained in less than four iterations.

The current densities of CO and H<sub>2</sub> predicted over Ag(110) by multiscale simulation are compared to those measured experimentally over a polycrystalline Ag foil (9). The (110) facet of Ag was used in the multiscale simulation because it is the most active facet of Ag (10) and found in higher relative abundance than (111) facets on polycrystalline Ag foils (51).

## 3. Results and Discussion

### 3.1 Identification of Free Energy Profile and Mechanisms for CO<sub>2</sub>RR and HER

Figure 2 shows three different reaction mechanisms for CO<sub>2</sub>RR and HER over Ag(110). The mechanism of HER involves adsorption of H<sub>2</sub>O followed by the transfer of one electron to <sup>\*</sup>H<sub>2</sub>O (Volmer step) to produce <sup>\*</sup>H with the instantaneous release of OH<sup>-</sup> and an Ag site. The second electron transfer to a free H<sub>2</sub>O in association with <sup>\*</sup>H (Heyrovsky step) releases another OH<sup>-</sup> to produce <sup>\*</sup>H<sub>2</sub> and an Ag site. H<sub>2</sub> desorbs into the electrolyte and phase-separates to produce gas bubbles. The barrier for the Volmer step with adsorbed H<sub>2</sub>O is lower than that with free H<sub>2</sub>O. The Tafel step is not energetically favored due to the large interatomic spacing

between  $^*\text{H}$  and  $^*\text{H}$  on Ag(110). Therefore, the rate of HER is dependent on the adsorption energies of  $\text{H}_2\text{O}$  and  $\text{H}_2$ , and the activation barriers for the Volmer and Heyrovsky steps. Figure 3a shows that  $\text{H}_2$  and  $\text{H}_2\text{O}$  are weakly bonded to Ag(110) with bonding energies -0.16 eV and -0.13 eV, respectively, at -0.6 V vs RHE. Their absolute bonding energy increases by  $\sim 0.02$  eV upon decreasing the potential from -0.6 V to -1.1 V vs RHE. This small increase in bonding energy is due to the higher energies of the LUMO antibonding orbitals of  $\text{H}_2$  and  $\text{H}_2\text{O}$  compared to those of CO and  $\text{CO}_2$ . Figure 3b shows the free energies of intermediates and reaction barriers for the Volmer and Heyrovsky steps evaluated at -0.9, -1.0, and -1.1 V vs RHE. At -1 V vs RHE, the energy barrier for Volmer step is 0.52 eV and the Heyrovsky step is 0.72 eV. The calculated transfer coefficients (the slope of the free energy vs potential plots) for the Volmer and Heyrovsky steps are 0.23 and 0.05, respectively. Since the Heyrovsky step has the highest free energy barrier, it is the rate-limiting reaction for HER over Ag.

The  $\text{CO}_2\text{RR}$  begins with the diffusion of dissolved  $\text{CO}_2$  across the hydrodynamic boundary layer and its adsorption via coordination of the C atom with the Ag atoms located at the trough sites of the (110) surface. The slightly distorted adsorbed  $\text{CO}_2$  ( $^*\text{CO}_2$ ), shown in Figure S5A, is stabilized by a donation from the highest occupied  $d$  orbital of Ag to the LUMO antibonding orbital of  $\text{CO}_2$ , this leads to a weakened C=O bond in which the oxygen participates in hydrogen bonding with water. Figure 2a and 2b show that  $^*\text{CO}_2$  is reduced to  $^{**}\text{COOH}$  which is then reduced to  $^*\text{CO}$  using  $^*\text{H}$  or  $^{**}\text{H}_2\text{O}$ , respectively. Formation of a  $^*\text{CO}_2$  anion ( $^*\text{CO}_2^{\delta-}$ ) was not considered in Figure 2a and 2b because the free energy barrier for conversion of  $^*\text{CO}_2^{\delta-}$  to  $^{**}\text{COOH}$  was at least 0.5 eV higher than the direct reduction of  $^*\text{CO}_2$  to  $^{**}\text{COOH}$ . In the case of reaction mechanism 1 (RM-1), the two elementary reactions of  $\text{CO}_2\text{RR}$  compete with the Heyrovsky reaction for  $^*\text{H}$ , whereas in RM-2 the  $\text{CO}_2\text{RR}$  competes with the Volmer reaction. RM-3 considers the formation of  $^*\text{CO}_2^{\delta-}$  (see Figure S5B) by partial electron transfer to  $^*\text{CO}_2$  as the free energy barrier for reduction of  $^*\text{CO}_2^{\delta-}$  is at least 1 eV lower than that for the reduction of  $^*\text{CO}_2$ . The hydrogen donor in RM-3 is taken to be free  $\text{H}_2\text{O}$ . The CO desorbed from the Ag electrode is assumed to readily desorb and form gas bubbles. Therefore, the rate of  $\text{CO}_2\text{RR}$  is dependent on the adsorption energies of  $\text{CO}_2$  and CO, and the free energy barriers for the elementary reactions.

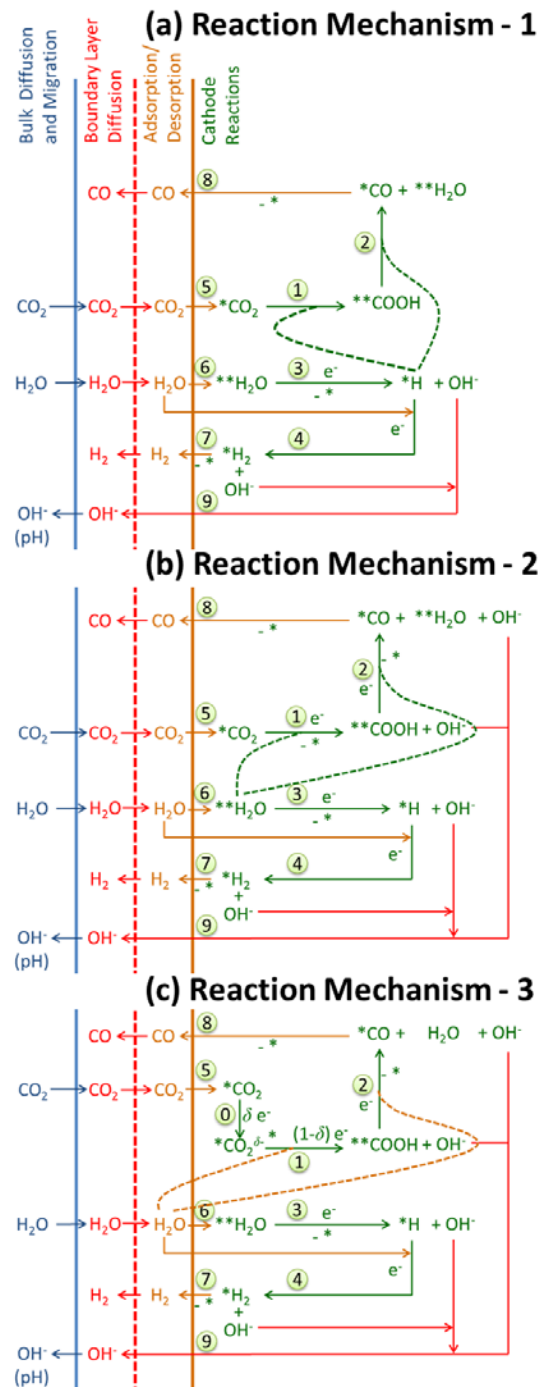


Figure 2: Three plausible reaction mechanisms (RMs) for the CO<sub>2</sub>RR and one for the HER occurring over Ag(110). The HER follows the Volmer-Heyrovsky reaction, whereas CO<sub>2</sub>RR can proceed via three different hydrogen donors such as \*H (RM-1), \*\*H<sub>2</sub>O (RM-2) or free H<sub>2</sub>O (RM-3). RM-1 and RM-2 have 9 elementary reactions and 7 species. RM-3 has 10 elementary reactions and 8 species. Reactions 0, 1, and 2 represent CO<sub>2</sub>RR; reactions 3 and 4 represent HER; reactions 5, 6, 7, and 8 represent quasi-equilibrium for reactants and products; and reaction 9 shows the direct release of OH<sup>-</sup> to the bulk electrolyte, as it does not adsorb to the cathode.

Figure 3a shows that the adsorption free energy for CO<sub>2</sub> increases from -0.25 eV to -0.30 eV as the potential decreases from -0.6 V to -1.1 V vs RHE. However, the adsorption free energy (or bonding energy) of CO decreases from -0.29 eV to -0.27 eV over the same range of applied potentials. The small increase in CO<sub>2</sub> adsorption energy is due to stronger  $\pi^*$  back-bonding, whereas the decrease in the bonding energy of \*CO is due to the increase in the energy level of the  $\pi^*$  orbital of CO. Such variation in the CO adsorption energy can be related to the measured low-wavenumber shifts in CO stretching frequency with decreasing potential.<sup>(35)</sup> Figure 3c shows the free energy profiles for the elementary steps for the CO<sub>2</sub>RR according to RM-1, RM-2, and RM-3 at -1 V vs RHE. The highest barrier and hence the rate-limiting step in all three cases corresponds to the formation of \*\*COOH. The energy barrier to produce \*\*COOH is 0.11 eV for RM-1, 0.41 eV for RM-2, and 0.43 eV for RM-3. However, the predicted current density decreases in the order RM-3 > RM-2 > RM-1 (see Figure 3d) at 1 atm of CO<sub>2</sub>, which is opposite to the expected order based on the values of the free energy activation barriers for \*\*COOH formation. The rate of reaction or current density is directly proportional to the concentration of hydrogen-donor species and exponentially dependent on the energy barriers. At -1 V vs RHE and 1 atm CO<sub>2</sub>, the coverage of \*H in RM-1 is  $1.6 \times 10^{-8}$ , the coverage of \*\*H<sub>2</sub>O in RM-2 is  $1.2 \times 10^{-3}$ , and the concentration of H<sub>2</sub>O in RM-3 is 55 M. The higher surface coverage of hydrogen-donors in RM-3 offsets the higher free energy of activation to yield the highest current density among the three mechanisms.

Figure 3d shows the variation in total current density with the partial pressure of CO<sub>2</sub>. RM-3 follows the same trend as the experimentally measured values. However, RM-1 and RM-2 both show an unphysical increase in CO current density with decreasing partial pressure of CO<sub>2</sub>. The rate of reaction is directly proportional to the product of the concentrations of \*CO<sub>2</sub> and \*H/\*\*H<sub>2</sub>O. Since \*CO<sub>2</sub> is the majority species, a slight decrease in the CO<sub>2</sub> concentration and hence the coverage of \*CO<sub>2</sub> can cause the coverage of minority species ( $<1 \times 10^{-5}$ ) such as \*H and \*\*H<sub>2</sub>O to increase by orders of magnitude, resulting in an overall increase in the rate of reaction. This result confirms that the highest energy pathway (RM-3) is the one that is consistent with experimental observation.

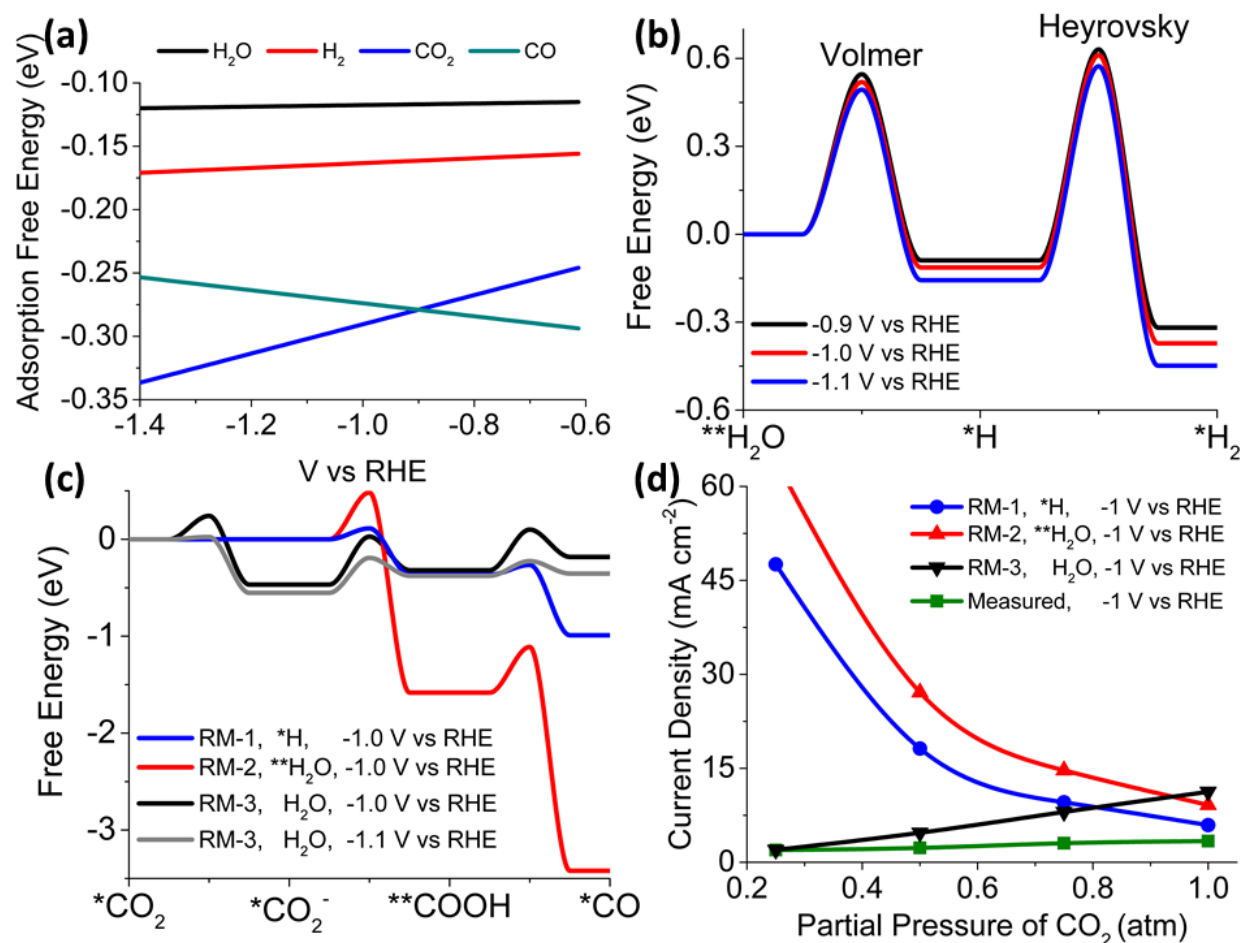


Figure 3: (a) Free energy of adsorption of H<sub>2</sub>O, H<sub>2</sub>, CO<sub>2</sub>, and CO on Ag(110) as a function of applied potential. (b) Free energy profile of the Volmer-Heyrovsky reaction to produce H<sub>2</sub> over Ag(110) at -0.9 V, -1.0 V, and -1.1 V vs RHE. (c) Free energy profile of the CO<sub>2</sub>RR over Ag(110) at -1.0 V vs RHE via three different reaction mechanism (RMs). The hydrogen donors in RM-1, RM-2, and RM-3 are \*H, \*\*H<sub>2</sub>O, and H<sub>2</sub>O, respectively. The free energy profile for RM-3 at -1.0 V and -1.1 V vs RHE is also shown. (d) Comparison of total current density simulated for RM-1, RM-2, and RM-3 over Ag(110) with the total current density measured over polycrystalline Ag foil at 0.25, 0.5, 0.75, 1 atm partial pressures of CO<sub>2</sub> in 0.1 M KHCO<sub>3</sub> electrolyte.

### 3.2 Intrinsic Kinetics of CO<sub>2</sub>RR over Ag and the Consequences of Polarization

The dependence of the intrinsic current densities for CO and H<sub>2</sub> produced over Ag(110) as a function of applied potential is illustrated in Figure 4(a) using RM-3. These calculations neglect the mass-transfer resistances and assume that for all potentials the concentration of CO<sub>2</sub> near the Ag cathode is at equilibrium with 1 atm of gaseous CO<sub>2</sub>. The intrinsic current density of CO is 12.3 mA cm<sup>-2</sup> at -1 V vs RHE, which is more than three times higher than that measured

experimentally ( $3.5 \text{ mA cm}^{-2}$ ) (9). The intrinsic current density can be fitted to a Butler-Volmer expression for which the exchange current density is  $1.71 \times 10^{-5} \text{ mA cm}^{-2}$ , the anodic transfer coefficient is 0.17, and the cathodic transfer coefficient is 0.49. The fitted transfer coefficients are  $< 0.5$ , which is within the range for most electrochemical reactions (52). The HER is completely suppressed during  $\text{CO}_2$  reduction as the free energy barrier for the Heyrovsky step is  $\sim 0.3 \text{ eV}$  higher than the barrier for  $^*\text{CO}_2^{\delta-}$  reduction reaction in RM-3. Figure 3c shows potential-dependent fractional coverages of adsorbates and intermediates for intrinsic reaction conditions. The dominant species on the Ag(110) surface are  $^*\text{CO}_2^{\delta-}$  and  $^*\text{H}$ , as species involved in the rate-limiting steps for CO and  $\text{H}_2$  formation, respectively. As the potential decreases below  $-0.75 \text{ V}$  vs RHE, the fractional coverage of  $^*\text{H}$  increases and all other species decreases. The sharp decrease in the coverages of  $^{**}\text{H}_2\text{O}$  and  $^{**}\text{COOH}$  is due to their consumption in the Volmer reaction and the reduction of  $^{**}\text{COOH}$ , which are much faster than the rates of the Heyrovsky reaction and the  $^*\text{CO}_2^{\delta-}$  reduction reaction. The decrease in  $^*\text{CO}$  coverage is due to the decrease in the adsorption energy of CO with decreasing potential (see Figure 3a).

Figure 4(b) shows the effect of mass-transfer on the calculated current densities of CO and  $\text{H}_2$  as a function of the potential applied to Ag(110). The current density for CO as shown in Figure 4(b) is significantly lower than that calculated in the absence of mass-transfer (Figure 4(a)) due to cathode polarization. This effect is a consequence of the increase in the concentration of  $\text{OH}^-$  (pH) and the consequent decrease in the concentration of  $\text{CO}_2$  during the CO2RR (8). The partial pressure of  $\text{CO}_2$  at the cathode decreases from 0.94 to 0.31 atm and the cathode pH increases from 6.8 to 7.5 as the potential decreases from  $-0.6 \text{ V}$  to  $-1.1 \text{ V}$  vs RHE. Figure 4(d) shows the variation in the fractional coverage due to polarization. At higher negative potentials, the coverages of carbon species decrease and the coverages of the hydrogen species increase due to the polarization of the cathode. The majority species at lower negative potentials are  $^*\text{CO}_2^{\delta-}$  and  $^{**}\text{COOH}$ , and at higher negative potentials are  $^*\text{H}$  and  $^*\text{CO}_2^{\delta-}$ . Our findings agree well with the recent IR spectroscopy of CO2RR over Ag, which show  $^{**}\text{COOH}$  as the majority species at lower negative potential and  $^*\text{CO}_2^{\delta-}$  as the major carbon-containing species at  $-1 \text{ V}$  vs RHE (37). The authors also report a very weak signal for  $^*\text{CO}$  during CO2RR, consistent with our simulation results. Figure 4(b) shows a slight increase in  $\text{H}_2$  current density at  $-1.1 \text{ V}$  vs RHE as compared to the intrinsic current density due to the increase in the  $^*\text{H}$  concentration caused by cathode polarization.

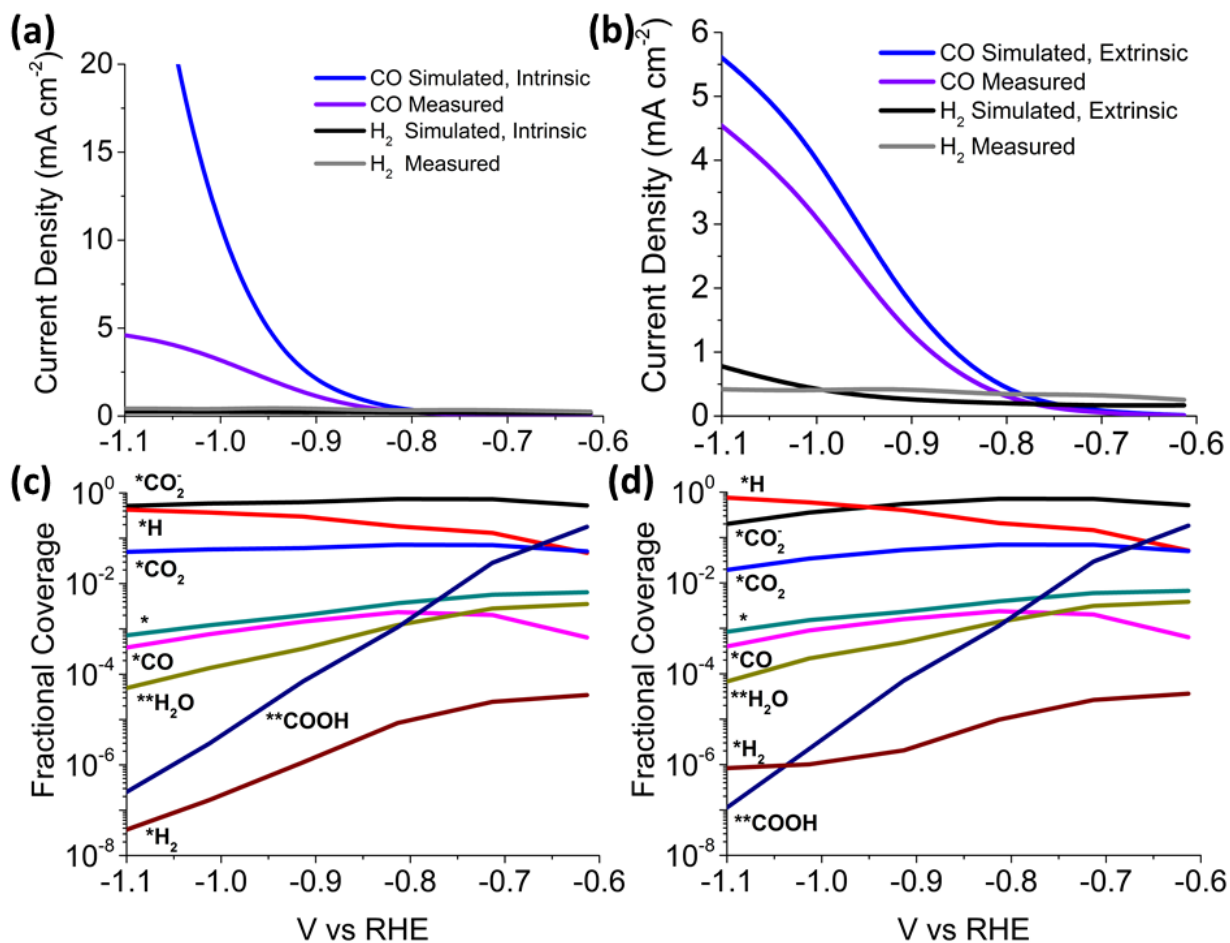


Figure 4: Comparison of simulated (a) intrinsic (without mass-transfer resistance) and (b) extrinsic (with mass-transport effects) current densities for RM-3 with the measured current densities of CO and H<sub>2</sub>. (c) The variation in the coverages of adsorbed and intermediate species with the applied potential under (c) intrinsic and (d) extrinsic conditions.

### 3.3 Effect of CO<sub>2</sub> Concentration and pH on the Kinetics

Figure 5(a) shows the increase in the intrinsic current density of CO with increasing partial pressure of CO<sub>2</sub> at -0.9 V, -1.0 V, and -1.1 V vs RHE. A power-law fit to these curves indicates that the intrinsic reaction order with respect to CO<sub>2</sub> is  $1.49 \pm 0.30$  at -0.9 V,  $1.63 \pm 0.19$  at -1.0 V, and  $1.83 \pm 0.09$  at -1.1 V. The intrinsic reaction order is greater than 1.0 because coverage of \*CO<sub>2</sub><sup>δ-</sup> (reactant for the rate-limiting step) decreases non-linearly with decreasing concentration of CO<sub>2</sub>. Since the adsorption free energy of CO<sub>2</sub> increases with decreasing potential (see Figure 3a), the reaction order increases with decreasing potential. The experimentally measured reaction orders are lower than the intrinsic reaction order due to the influence of mass-transfer. Figure 5(b) shows the extrinsic and measured current density of CO increases with increasing partial pressure of CO<sub>2</sub> at -1.0 V vs RHE. The measured current



density shown in Figure 5(b) was obtained from the cyclic voltammograms for the CO<sub>2</sub>RR over polycrystalline Ag for partial CO<sub>2</sub> pressures between 0.25 and 1 atm (9). These cyclic voltammograms were measured at a scan rate of 10 mV s<sup>-1</sup> in order to obtain quasi-steady-state current densities. By contrast, the simulated current densities in Figure 5(b) represents the steady-state product current densities for the CO<sub>2</sub>RR over Ag(110) obtained at a constant potential of -1 V vs RHE. The simulated apparent order is 1.58±0.32 and the measured apparent order is 1.56±0.23, indicating excellent agreement between the simulated and experimentally observed dependence on CO<sub>2</sub> partial pressure. Figure 5(c) shows that the intrinsic current density of H<sub>2</sub> decreases very slightly for pHs between 7 to 14. The intrinsic current density for CO also changes very little for pHs between 7 and 13, but then declines when the pH is increased to 14. This result suggests that the pH of electrolyte does not have a direct effect on the rates of CO<sub>2</sub>RR and HER in near-neutral pH electrolytes. However, the pH of the electrolyte can affect the solubility of CO<sub>2</sub> (8), which in turn affects the kinetics of CO<sub>2</sub>RR. This trend has been observed experimentally for the CO<sub>2</sub>RR over Cu (53) and Ag (9). The pH of the electrolyte may also affect the local orientation of H<sub>2</sub>O near the cathode, which can, in turn, affect the free energy barriers of CO<sub>2</sub>RR and HER (54).

### 3.4 Strategies to Increase Activity of CO<sub>2</sub>RR over Ag

The present analysis has shown that the rate-limiting step in CO<sub>2</sub>RR over Ag(110) is the reduction of \*CO<sub>2</sub><sup>δ-</sup>. \*CO<sub>2</sub><sup>δ-</sup> is stabilized by back-donation of electrons from highest occupied *d* orbital of the metal to the lowest unoccupied π\* antibonding orbital of CO<sub>2</sub>. The addition of electrons to the anti-bonding orbital weakens the C-O bond and facilitates the reduction of \*CO<sub>2</sub><sup>δ-</sup> to \*COOH. The negative anion \*CO<sub>2</sub><sup>δ-</sup> can be stabilized by the electrostatic interactions with the cations.(34) Although the magnitude of such interactions is limited by the size and the concentration of cations, it can boost the reaction rates by at least two fold.(14) Another strategy to stabilize \*CO<sub>2</sub><sup>δ-</sup> is to create grain boundaries and under coordinated sites on the surface of the metal. Such strategies have shown much higher increase in the CO<sub>2</sub> reduction current densities over Cu.(55)

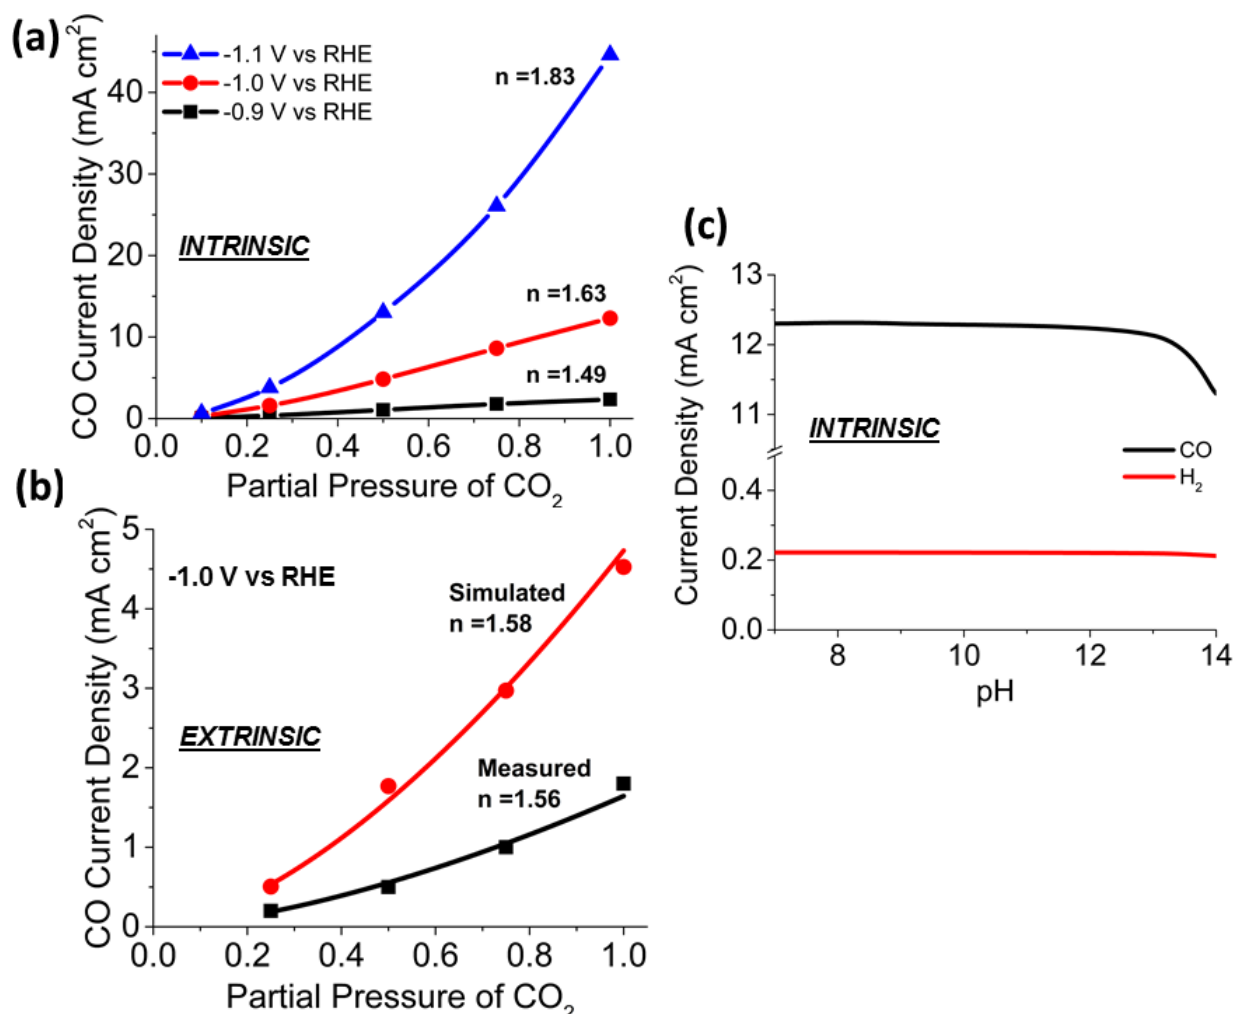


Figure 5: (a) Increase in the intrinsic CO current density with increasing partial pressure of CO<sub>2</sub>. The intrinsic reaction order with respect to CO<sub>2</sub> is 1.49 at -0.9 V vs RHE, 1.63 at -1.0 V vs RHE, and 1.83 at -1.1 V vs RHE. (b) Increase in the extrinsic CO current density with increasing partial pressure of CO<sub>2</sub>. The measured current density was obtained from cyclic voltammogram of CO<sub>2</sub>RR over polycrystalline Ag at -1 V vs RHE. The simulated apparent reaction order of 1.58 agrees well with the measured apparent order of 1.56. (c) The decrease in the CO and H<sub>2</sub> current densities with increasing pH of the electrolyte.

#### 4. Conclusions and Perspectives

This work clearly demonstrates that in order to identify a physically correct mechanism for the electrochemical reduction of CO<sub>2</sub> and the dependence of the rate of product formation on the cathode voltage and partial pressure of CO<sub>2</sub>, it is essential to simulate all aspects of the electrochemical system, and not just the cathode surface chemistry. Such a multiscale, multiphysics model was developed in the present study. Equilibrium constants and rate

coefficients for processes occurring on the cathode surface were determined from DFT calculations of the free energies of adsorption and reaction, and the free energies of activation for all elementary processes. This information was used to determine equilibrium constants and rate coefficient for a microkinetic model that describes the current densities for H<sub>2</sub> and CO. The concentration of all species at the cathode and anode surfaces was determined from a continuum model that takes into account the transport of all neutral and ionic species by diffusion and migration as well as the interconversion of anionic species.

The model developed here was used to predict the formation of H<sub>2</sub> and CO in an electrochemical cell that contains an Ag(110) surface as the cathode, a polycrystalline Pt foil as the anode, a Selemion, anion conducting membrane separator. The lowest energy pathway for the HER was identified to be a Volmer-Heyrovsky sequence, for which the Heyrovsky is the rate-limiting step. Three different mechanisms for the CO<sub>2</sub>RR were considered (RM-1, RM-2, and RM-3), which differ in the nature of the hydrogen donor - \*H, \*\*H<sub>2</sub>O, and free H<sub>2</sub>O. In all three cases, the hydrogenation of adsorbed CO<sub>2</sub> to produce \*\*COOH is the rate-limiting step for producing CO. The barrier for this step increases in the order RM-1 < RM-2 < RM-3. Remarkably, while RM-3 exhibits the highest barrier for hydrogenation of adsorbed CO<sub>2</sub>, this is the only mechanism that correctly predicts the dependence of the current density on the applied cathode voltage and the partial pressure of CO<sub>2</sub>. It is notable that this unexpected finding would not have been possible without the use of a multiscale, multiphysics model to simulate the overall cell performance. The majority adsorbed species in RM-3 are predicted to be \*CO<sub>2</sub><sup>δ-</sup>, \*\*COOH, and \*H; and the minority species are predicted to be \*CO<sub>2</sub> and \*CO. These predictions are in strong qualitative agreement with what has been recently reported in an *in situ* IR spectroscopic investigation of the CO<sub>2</sub>RR over Ag(37). Previous theoretical efforts were able to predict only the onset potentials of the CO<sub>2</sub>RR over Ag(111) using a pseudo steady-state microkinetic model with rate parameters obtained from DFT calculations (34). Here we have shown for the first time a full prediction of current densities, Faradaic efficiencies, and surface coverages as a function of applied potentials for CO<sub>2</sub>RR over Ag. The predictions of these simulations compare very well with the experimental data because the multiscale model accounts for all essential physical phenomena, occurring over a wide range of length and time scales, that influence the dynamics of the CO<sub>2</sub>RR. We also find that cathode polarization reduces the intrinsic current density significantly for cathode voltages above ~ -0.9 V vs RHE. When the effects of cathode polarization are taken into account, the simulated extrinsic current density matches well with that measured experimentally, further validating the model(9). The simulated apparent order of CO<sub>2</sub>RR with respect to the partial pressure of CO<sub>2</sub> at - 1 V vs RHE is 1.58, which agrees very well with the observed value of 1.56(9). In summary, we have demonstrated that the multiscale approach developed in this study should be used to assess the validity of reaction mechanisms proposed for the CO<sub>2</sub>RR under the circumstance where electrolyte polarization is unavoidable and can influence the pH and CO<sub>2</sub> concentration near the cathode surface.

## Acknowledgements

This work was performed at the Materials and Systems Engineering Lab at the University of Illinois at Chicago and the Joint Center for Artificial Photosynthesis, a DOE Energy Innovation Hub, supported through the Office of Science of the U.S. Department of Energy under Award number DE-SC0004993. M.R.S acknowledges financial support from the University of Illinois at Chicago.

## References

1. Chu S & Majumdar A (2012) Opportunities and challenges for a sustainable energy future. *nature* 488(7411):294-303.
2. Graves C, Ebbesen SD, Mogensen M, & Lackner KS (2011) Sustainable hydrocarbon fuels by recycling CO<sub>2</sub> and H<sub>2</sub>O with renewable or nuclear energy. *Renewable and Sustainable Energy Reviews* 15(1):1-23.
3. Singh MR, Clark EL, & Bell AT (2015) Thermodynamic and achievable efficiencies for solar-driven electrochemical reduction of carbon dioxide to transportation fuels. *Proceedings of the National Academy of Sciences* 112(45):E6111-E6118.
4. Hori Y (2008) Electrochemical CO<sub>2</sub> reduction on metal electrodes. *Modern aspects of electrochemistry*, (Springer), pp 89-189.
5. Sullivan BP, Krist K, & Guard H (2012) *Electrochemical and electrocatalytic reactions of carbon dioxide* (Elsevier).
6. Singh MR & Bell AT (2016) Design of an artificial photosynthetic system for production of alcohols in high concentration from CO<sub>2</sub>. *Energy & Environmental Science* 9(1):193-199.
7. van de Loosdrecht J & Niemantsverdriet JH eds (2013) *Synthesis Gas to Hydrogen, Methanol, and Synthetic Fuels* (De Gruyter, Berlin, Berlin).
8. Singh MR, Clark EL, & Bell AT (2015) Effects of electrolyte, catalyst, and membrane composition and operating conditions on the performance of solar-driven electrochemical reduction of carbon dioxide. *Physical Chemistry Chemical Physics* 17(29):18924-18936.
9. Hatsukade T, Kuhl KP, Cave ER, Abram DN, & Jaramillo TF (2014) Insights into the electrocatalytic reduction of CO<sub>2</sub> on metallic silver surfaces. *Physical Chemistry Chemical Physics* 16(27):13814-13819.
10. Hoshi N, Kato M, & Hori Y (1997) Electrochemical reduction of CO<sub>2</sub> on single crystal electrodes of silver Ag (111), Ag (100) and Ag (110). *Journal of electroanalytical chemistry* 440(1-2):283-286.
11. Salehi-Khojin A, *et al.* (2013) Nanoparticle silver catalysts that show enhanced activity for carbon dioxide electrolysis. *The Journal of Physical Chemistry C* 117(4):1627-1632.
12. Lu Q, *et al.* (2014) A selective and efficient electrocatalyst for carbon dioxide reduction. *Nature communications* 5:3242.
13. Rosen BA, *et al.* (2011) Ionic liquid-mediated selective conversion of CO<sub>2</sub> to CO at low overpotentials. *Science* 334(6056):643-644.
14. Singh MR, Kwon Y, Lum Y, Ager III JW, & Bell AT (2016) Hydrolysis of Electrolyte Cations Enhances the Electrochemical Reduction of CO<sub>2</sub> over Ag and Cu. *Journal of the American Chemical Society* 138(39):13006-13012.

15. Thorson MR, Siil KI, & Kenis PJ (2013) Effect of Cations on the Electrochemical Conversion of CO<sub>2</sub> to CO. *Journal of the Electrochemical Society* 160(1):F69-F74.
16. Verma S, Lu X, Ma S, Masel RI, & Kenis PJ (2016) The effect of electrolyte composition on the electroreduction of CO<sub>2</sub> to CO on Ag based gas diffusion electrodes. *Physical Chemistry Chemical Physics* 18(10):7075-7084.
17. Kim B, Ma S, Jhong H-RM, & Kenis PJ (2015) Influence of dilute feed and pH on electrochemical reduction of CO<sub>2</sub> to CO on Ag in a continuous flow electrolyzer. *Electrochimica Acta* 166:271-276.
18. Azuma M, Hashimoto K, Hiramoto M, Watanabe M, & Sakata T (1990) Electrochemical Reduction of Carbon Dioxide on Various Metal Electrodes in Low-Temperature Aqueous KHCO<sub>3</sub> Media. *Journal of the Electrochemical Society* 137(6):1772-1778.
19. Lobaccaro P, *et al.* (2016) Effects of temperature and gas-liquid mass transfer on the operation of small electrochemical cells for the quantitative evaluation of CO<sub>2</sub> reduction electrocatalysts. *Physical Chemistry Chemical Physics* 18(38):26777-26785.
20. Hara K, Kudo A, & Sakata T (1995) Electrochemical reduction of carbon dioxide under high pressure on various electrodes in an aqueous electrolyte. *Journal of Electroanalytical Chemistry* 391(1-2):141-147.
21. Ivan TT (1963) Reversed fuel cell and oxygen generator. U. S. Patent No. 3,085,053.
22. Taniguchi I, Aurian-Blajeni B, & Bockris JOM (1983) Photo-aided reduction of carbon dioxide to carbon monoxide. *Journal of electroanalytical chemistry and interfacial electrochemistry* 157(1):179-182.
23. Lieber CM & Lewis NS (1984) Catalytic reduction of CO<sub>2</sub> at carbon electrodes modified with cobalt phthalocyanine. *J. Am. Chem. Soc* 106(17):5033-5034.
24. Hori Y, Kikuchi K, & Suzuki S (1985) Production of CO and CH<sub>4</sub> in electrochemical reduction of CO<sub>2</sub> at metal electrodes in aqueous hydrogencarbonate solution. *Chemistry Letters* 14(11):1695-1698.
25. Noda H, *et al.* (1990) Electrochemical reduction of carbon dioxide at various metal electrodes in aqueous potassium hydrogen carbonate solution. *Bulletin of the Chemical Society of Japan* 63(9):2459-2462.
26. Kortlever R, Shen J, Schouten KJP, Calle-Vallejo F, & Koper MT (2015) Catalysts and reaction pathways for the electrochemical reduction of carbon dioxide. *The journal of physical chemistry letters* 6(20):4073-4082.
27. Asadi M, *et al.* (2016) Nanostructured transition metal dichalcogenide electrocatalysts for CO<sub>2</sub> reduction in ionic liquid. *Science* 353(6298):467-470.
28. Hori Y, Wakebe H, Tsukamoto T, & Koga O (1994) Electrocatalytic process of CO selectivity in electrochemical reduction of CO<sub>2</sub> at metal electrodes in aqueous media. *Electrochimica Acta* 39(11-12):1833-1839.
29. Schwarz HA & Dodson RW (1989) Reduction potentials of CO<sub>2</sub><sup>-</sup> and the alcohol radicals. *The Journal of Physical Chemistry* 93(1):409-414.
30. Ikeda S, Takagi T, & Ito K (1987) Selective formation of formic acid, oxalic acid, and carbon monoxide by electrochemical reduction of carbon dioxide. *Bulletin of the Chemical Society of Japan* 60(7):2517-2522.
31. Gennaro A, *et al.* (1996) Mechanism of the electrochemical reduction of carbon dioxide at inert electrodes in media of low proton availability. *Journal of the Chemical Society, Faraday Transactions* 92(20):3963-3968.

32. Kostecki R & Augustynski J (1994) Electrochemical reduction of CO<sub>2</sub> at an activated silver electrode. *Berichte der Bunsengesellschaft für physikalische Chemie* 98(12):1510-1515.
33. Rosen J, *et al.* (2015) Mechanistic insights into the electrochemical reduction of CO<sub>2</sub> to CO on nanostructured Ag surfaces. *Acs Catalysis* 5(7):4293-4299.
34. Chen LD, Urushihara M, Chan K, & Nørskov JK (2016) Electric Field Effects in Electrochemical CO<sub>2</sub> Reduction. *ACS Catalysis* 6(10):7133-7139.
35. Oda I, Ogasawara H, & Ito M (1996) Carbon monoxide adsorption on copper and silver electrodes during carbon dioxide electroreduction studied by infrared reflection absorption spectroscopy and surface-enhanced raman spectroscopy. *Langmuir* 12(4):1094-1097.
36. Ichinohe Y, Wadayama T, & Hatta A (1995) Electrochemical reduction of CO<sub>2</sub> on silver as probed by surface-enhanced Raman scattering. *Journal of Raman Spectroscopy* 26(5):335-340.
37. Firet NJ & Smith WA (2017) Probing the reaction mechanism of CO<sub>2</sub> electroreduction over Ag films via operando infrared spectroscopy. *ACS Catalysis* 7(1):606-612.
38. Hori Y, Murata A, & Takahashi R (1989) Formation of hydrocarbons in the electrochemical reduction of carbon dioxide at a copper electrode in aqueous solution. *Journal of the Chemical Society, Faraday Transactions 1: Physical Chemistry in Condensed Phases* 85(8):2309-2326.
39. Le XT (2008) Permselectivity and microstructure of anion exchange membranes. *Journal of colloid and interface science* 325(1):215-222.
40. Kiss AM, *et al.* (2013) Carbonate and bicarbonate ion transport in alkaline anion exchange membranes. *Journal of The Electrochemical Society* 160(9):F994-F999.
41. Herrera A & Yeager H (1987) Halide and sulfate ion diffusion in Nafion membranes. *Journal of The Electrochemical Society* 134(10):2446-2451.
42. Huang K-L, Holsen TM, & Selman JR (2003) Anion partitioning in and diffusion through a Nafion membrane. *Industrial & engineering chemistry research* 42(15):3620-3625.
43. Birss VI & Damjanovic A (1983) A study of the anomalous pH dependence of the oxygen evolution reaction at platinum electrodes in acid solutions. *Journal of The Electrochemical Society* 130(8):1694-1699.
44. Letchworth-Weaver K & Arias T (2012) Joint density functional theory of the electrode-electrolyte interface: Application to fixed electrode potentials, interfacial capacitances, and potentials of zero charge. *Physical Review B* 86(7):075140.
45. Mathew K, Sundararaman R, Letchworth-Weaver K, Arias T, & Hennig RG (2014) Implicit solvation model for density-functional study of nanocrystal surfaces and reaction pathways. *The Journal of chemical physics* 140(8):084106.
46. Goodpaster JD, Bell AT, & Head-Gordon M (2016) Identification of Possible Pathways for C–C Bond Formation during Electrochemical Reduction of CO<sub>2</sub>: New Theoretical Insights from an Improved Electrochemical Model. *The journal of physical chemistry letters* 7(8):1471-1477.
47. Gajdoš M, Eichler A, & Hafner J (2004) CO adsorption on close-packed transition and noble metal surfaces: trends from ab initio calculations. *Journal of Physics: Condensed Matter* 16(8):1141.

48. Luo S, Zhao Y, & Truhlar DG (2012) Improved CO Adsorption energies, site preferences, and surface formation energies from a meta-generalized gradient approximation exchange–correlation functional, M06-L. *The journal of physical chemistry letters* 3(20):2975-2979.
49. Zheng J, Zhao Y, & Truhlar DG (2007) Representative benchmark suites for barrier heights of diverse reaction types and assessment of electronic structure methods for thermochemical kinetics. *Journal of chemical theory and computation* 3(2):569-582.
50. Nørskov JK, Abild-Pedersen F, Studt F, & Bligaard T (2011) Density functional theory in surface chemistry and catalysis. *Proceedings of the National Academy of Sciences* 108(3):937-943.
51. Schubert H, *et al.* (1995) On the relation between catalytic performance and microstructure of polycrystalline silver in the partial oxidation of methanol. *Catalysis letters* 33(3):305-319.
52. Newman J & Thomas-Alyea KE (2012) *Electrochemical systems* (John Wiley & Sons).
53. Kas R, Kortlever R, Yilmaz H, Koper M, & Mul G (2015) Manipulating the hydrocarbon selectivity of copper nanoparticles in CO<sub>2</sub> electroreduction by process conditions. *ChemElectroChem* 2(3):354-358.
54. Durst J, *et al.* (2014) New insights into the electrochemical hydrogen oxidation and evolution reaction mechanism. *Energy & Environmental Science* 7(7):2255-2260.
55. Li CW & Kanan MW (2012) CO<sub>2</sub> reduction at low overpotential on Cu electrodes resulting from the reduction of thick Cu<sub>2</sub>O films. *Journal of the American Chemical Society* 134(17):7231-7234.